

Superconducting States in Frustrating t - J Model: A Model Connecting High- T_c Cuprates, Organic Conductors and Na_xCoO_2

Masao OGATA*

*Department of Physics, University of Tokyo,
7-3-1, Hongo, Bunkyo-ku, Tokyo 113-0033 Japan*

(Received February 2, 2008)

The two-dimensional t - J model on a frustrating lattice is studied using mean-field variational theories with Gutzwiller approximation. We find that a superconducting state with broken time-reversal symmetry (d+id state) is realized in the parameter region close to the triangular lattice. The frustration enlarges the region of superconductivity when $t < 0$ for the hole-doped case, which is equivalent to $t > 0$ for electron doping. We also discuss the SU(2) degeneracy at half-filling. The d+id state probably corresponds to the spin gap state at half-filling.

KEYWORDS: Frustration, t - J model, time-reversal symmetry breaking, Gutzwiller approximation

Frustration is an interesting problem and has been extensively studied in spin systems. The effect of frustration in itinerant electron systems, however, is not so well understood. Resonating-valence bond (RVB) state, which is a liquid state consisting of spin-singlet bonds, was originally discussed in the Heisenberg model on a triangular lattice where the frustration was expected to destroy the long-range magnetic order leading to a quantum spin-liquid.^{1,2)} It was speculated that the carrier doping to the spin system will induce the RVB states which are directly related to superconductivity.³⁾ Thus it is very important to investigate where the RVB states are realized in frustrated systems.

Recently it has become possible to dope carriers in the two-dimensional organic conductor, κ -(BEDT-TTF)₂X, which has a lattice structure very similar to the triangular lattice. Actually it shows superconductivity under pressure.⁴⁾ More recently, a superconductivity has been discovered in Na_xCoO_2 compounds, in which Co atoms form layered triangular lattices.⁵⁾ Although the superconducting properties in these materials have not been clarified yet, it is very interesting to study the possibility of RVB-type superconductivity in a model which has the effect of frustration. In this paper we study the t - J model on a lattice as shown in Fig. 1, which interpolates between the square and triangular lattices. The organic conductors have such lattice structures.

In the case of high- T_c superconductivity, hole doping to the square Heisenberg spin system induces d_{x²-y²}-wave RVB-type superconductivity.⁶⁻¹⁰⁾ On the other hand, in the triangular lattice, the analysis of high-temperature expansion of the free energy suggests that the doping induces an RVB state when the hopping integral t is positive for the hole-doped case.¹¹⁾ (Note that this corresponds to $t < 0$ for electron-doped case.) When $t < 0$, the competition between the ferromagnetic tendency and singlet formation was observed. In this paper, in order to study the possibility of superconductivity in the ground state, we use a variational theory with Gutzwiller approximation.^{8,10)} We find that the frustration enlarges the region of superconductivity when

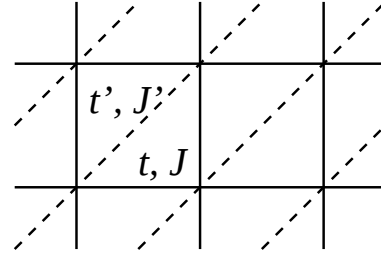


Fig. 1. Lattice structure of the frustrated two-dimensional t - J model. On the bonds forming the square lattice (solid lines), we have t and J terms. t' and J' terms are defined on the diagonal bonds (dashed lines).

$t < 0$, and that a superconducting state with broken time-reversal symmetry (chiral state) is realized in the parameter region close to the triangular lattice. We also discuss the SU(2) degeneracy at half-filling.

The t - J model on a lattice in Fig. 1 is written as

$$\mathcal{H} = -t \sum_{\langle i,j \rangle \sigma} P_G (c_{i\sigma}^\dagger c_{j\sigma} + \text{H.c.}) P_G + J \sum_{\langle i,j \rangle} \mathbf{S}_i \cdot \mathbf{S}_j - t' \sum_{\langle i,j \rangle \sigma} P_G (c_{i\sigma}^\dagger c_{j\sigma} + \text{H.c.}) P_G + J' \sum_{\langle i,j \rangle} \mathbf{S}_i \cdot \mathbf{S}_j, \quad (1)$$

where $P_G = \prod_i (1 - n_{i\uparrow} n_{i\downarrow})$ is the Gutzwiller projection operator which excludes double occupancies. $\langle i, j \rangle$ and $\langle i, j \rangle$ represent the summation over nearest-neighbor and one of the next-nearest neighbor pairs as shown in Fig. 1, respectively. The sign of t is crucial since there is no electron-hole symmetry.¹¹⁾ Hereafter we use $|t|$ as an energy unit and study the parameter range, $t'/t = J'/J = 0.0$ -1.0. The model becomes the square lattice t - J model when $J'/J = 0$; and the triangular lattice when $J'/J = 1$.

For this Hamiltonian, we consider Gutzwiller-type variational wave function $P_G |\Phi\rangle$ with $|\Phi\rangle$ representing a BCS mean-field wave function. For estimating the variational energy, we use the Gutzwiller approximation in which the effect of the projection is replaced by a statis-

* E-mail address: ogata@phys.s.u-tokyo.ac.jp

tical weight as follows^{8,10)}

$$\begin{aligned} \langle c_i^\dagger c_j \rangle &= g_t \langle c_i^\dagger c_j \rangle_0, \\ \langle \mathbf{S}_i \cdot \mathbf{S}_j \rangle &= g_s \langle \mathbf{S}_i \cdot \mathbf{S}_j \rangle_0. \end{aligned} \quad (2)$$

Here $\langle \dots \rangle_0$ represents the expectation value in terms of $|\Phi\rangle$, and $\langle \dots \rangle$ represents the normalized expectation value in $P_G|\Phi\rangle$. In the simplest Gutzwiller approximation we have

$$g_t = \frac{2\delta}{1+\delta}, \quad g_s = \frac{4}{(1+\delta)^2}, \quad (3)$$

where δ is the density of holes, i.e., the electron number is $n = 1 - \delta$. It has been shown that this approximation gives a fairly reliable estimation for the variational energy for the pure $d_{x^2-y^2}$ -wave superconducting state when it is compared with the variational Monte Carlo results.^{8,10)}

In order to search for the state with the lowest variational energy, we studied large unit cells assuming site dependent order parameters. In this Gutzwiller approximation, we can have order parameters,

$$\Delta_{ij} = \langle c_{i\uparrow}^\dagger c_{j\downarrow}^\dagger \rangle_0, \quad \chi_{ij\sigma} = \langle c_{i\sigma}^\dagger c_{j\sigma} \rangle_0. \quad (4)$$

We assume $\chi_{ij\uparrow} = \chi_{ij\downarrow} = \chi_{ij}$ and that Δ_{ij} is a singlet pairing, i.e., $\Delta_{ij} = \Delta_{ji}$. By minimizing the variational energy we obtain a Bogoliubov-de Gennes equation¹²⁾ and self-consistency equations. We have tried various trial states and found that the uniform state is always stabilized except for some special states realized only very near half-filling. Since these special states may be an artifact of the mean-field-type calculations,¹³⁾ they are not discussed in this paper. The obtained phase diagrams for $J/t = 0.3$, $J'/t' = 0.3$ are shown in Fig. 2 as a function of the ratio J'/J and the electron density n .

We find that in the region with $J'/J < 0.675$ the $d_{x^2-y^2}$ -wave superconducting state is stabilized. This state is the same as in the square lattice case ($J' = 0$). When J'/J exceeds 0.675 a superconducting state with imaginary part of order parameter appears, which we call as d+id state as shown in Fig. 2. Since there is no continuous symmetry in our model, the notation of d+id-wave just represents a discretized version of $d_{x^2-y^2}$ -id $_{xy}$ -wave superconductivity. The detailed analysis is shown later. This state has excitation gaps all over the fermi surface and breaks time reversal symmetry. Another interesting feature is that for $t < 0$ the superconducting region increases as J'/J becomes large, while its region decreases when $t > 0$.

Before discussing the superconducting properties, let us here clarify the SU(2) degeneracy realized at half-filling in the present model. By solving the Bogoliubov-de Gennes equations we find various states at half-filling which have exactly the same variational energy with each other. For the uniform state, we have the energy dispersion for quasiparticles as

$$E_k = \sqrt{\varepsilon_k^2 + |F_k|^2}, \quad (5)$$

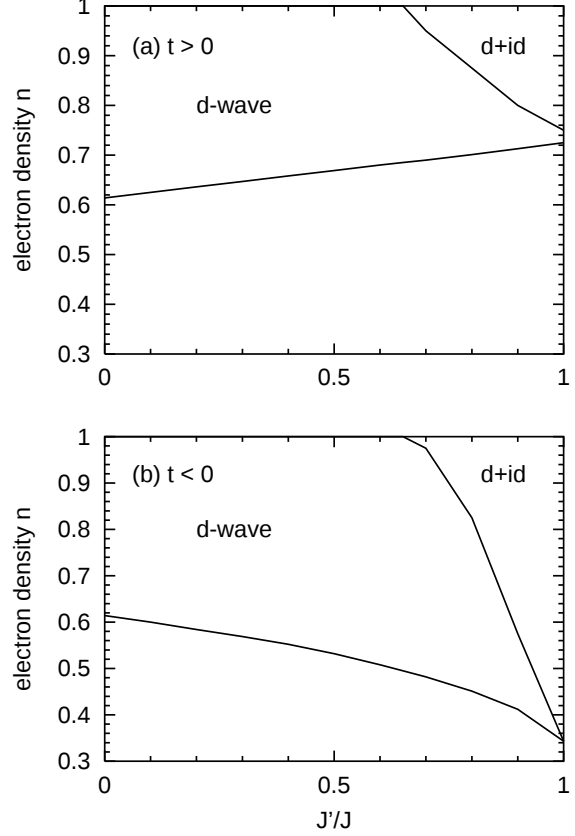


Fig. 2. Phase diagram obtained in Gutzwiller approximation of the RVB states in the frustrated two-dimensional t - J model with (a) positive t and (b) negative t . $J/|t| = 0.3$ and $J'/|t'| = 0.3$.

where

$$\varepsilon_k = -\frac{3}{2}g_s J(\chi_x \cos k_x + \chi_y \cos k_y) - \frac{3}{2}g_s J' \chi_{xy} \cos(k_x + k_y), \quad (6)$$

$$F_k = \frac{3}{2}g_s J(\Delta_x e^{-i\theta} \cos k_x + \Delta_y e^{i\theta'} \cos k_y) + \frac{3}{2}g_s J' \Delta_{xy} \cos(k_x + k_y). \quad (7)$$

Here Δ_x (Δ_y) is the superconducting order parameter on the bonds in the x -(y)-direction, and Δ_{xy} is in the diagonal direction. We denote θ (θ') as the phase of the order parameter relative to that on the diagonal bonds. Note that, in this notation, the pure $d_{x^2-y^2}$ -wave state is represented as $\Delta_x = \Delta_y$, $\Delta_{xy} = 0$ and $\theta = \theta' = \pi/2$.

We find that, in each energetically degenerate state, these parameters satisfy the following relations;

$$\chi_x \chi_y + \Delta_x \Delta_y \cos(\theta + \theta') = 0, \quad (8a)$$

$$\chi_x \chi_{xy} + \Delta_x \Delta_{xy} \cos \theta = 0, \quad (8b)$$

$$\chi_y \chi_{xy} + \Delta_y \Delta_{xy} \cos \theta' = 0. \quad (8c)$$

In this case the energy dispersion becomes

$$E_k = \frac{3}{2}g_s \sqrt{J^2(\chi_x^2 + \Delta_x^2) \cos^2 k_x + J^2(\chi_y^2 + \Delta_y^2) \cos^2 k_y + J'^2(\chi_{xy}^2 + \Delta_{xy}^2)} \quad (9)$$

The self-consistency equations are

$$1 = \frac{1}{N} \sum_k \frac{\frac{3}{4} g_s J \cos^2 k_x}{E_k}, \quad (10a)$$

$$1 = \frac{1}{N} \sum_k \frac{\frac{3}{4} g_s J \cos^2 k_y}{E_k}, \quad (10b)$$

$$1 = \frac{1}{N} \sum_k \frac{\frac{3}{4} g_s J' \cos^2(k_x + k_y)}{E_k}, \quad (10c)$$

where N is the number of sites and the summation over $\mathbf{k}$ is in the Brillouin zone (in our model $-\pi \leq k_x, k_y \leq \pi$).

Since there are 8 parameters ($\chi_x, \chi_y, \chi_{xy}, \Delta_x, \Delta_y, \Delta_{xy}, \theta, \theta'$) and 6 equations (8) and (10), we have remaining two degrees of freedom which lead to the various states obtained at half-filling. This is an extension of the SU(2) degeneracy discussed in the square lattice ($J' = 0$).^{8,14} For example, one of the realized states at half-filling has

$$\begin{aligned} \chi_x = \chi_y = 0, \quad \chi_{xy} \neq 0, \quad \Delta_x = \Delta_y \neq 0, \quad \Delta_{xy} = 0, \\ \theta = \theta' = \frac{\pi}{4}. \end{aligned} \quad (11)$$

When $\chi_{xy} \rightarrow 0$, this state is naturally connected to the so-called d+is state realized in the square lattice. Another state with

$$\begin{aligned} \chi_x = \chi_y = \Delta_x = \Delta_y \neq 0, \\ \chi_{xy} = 0, \quad \Delta_{xy} \neq 0 \text{ and } \theta = \theta' = \frac{\pi}{2}, \end{aligned} \quad (12)$$

is connected to the $d_{x^2-y^2}$ -wave state for the square lattice.

Since these degenerate states have common values for

$$D = \sqrt{\chi_x^2 + \Delta_x^2} = \sqrt{\chi_y^2 + \Delta_y^2}, \quad (13)$$

$$D' = \sqrt{\chi_{xy}^2 + \Delta_{xy}^2}, \quad (14)$$

we plot their J'/J dependence in Fig. 3(a). As J'/J approaches to 1, D becomes equal to D' .

Next let us discuss the doped case. Once some holes are introduced, the above degeneracy is readily lifted, and the lowest non-degenerate state becomes the superconducting state which is shown in Fig. 2. We note that the flux phase proposed before^{7,15-18} is not stabilized. Since the order parameters are uniquely determined at finite δ , we determine the relative phase of the superconducting order parameters, θ and θ' , by taking the limit $\delta \rightarrow 0$. The obtained phase is shown in Fig. 3(b). When Δ_{xy} starts to have a finite value at $J'/J = 0.675$, the relative phases are $\theta = \theta' = \pi/2$. This means that a small component Δ_{xy} appears as an imaginary part ($i\Delta_{xy}$) in addition to the pure $d_{x^2-y^2}$ -wave state. As J'/J increases, the relative phase approaches to $2\pi/3$, and when $J' = J$ (triangular lattice) the three order parameters Δ_x, Δ_y and Δ_{xy} become symmetric with each other. This state is consistent with the other works.^{15,19} This gradual change of the relative phase gives a natural continuation between the $d_{x^2-y^2}$ -wave superconductivity

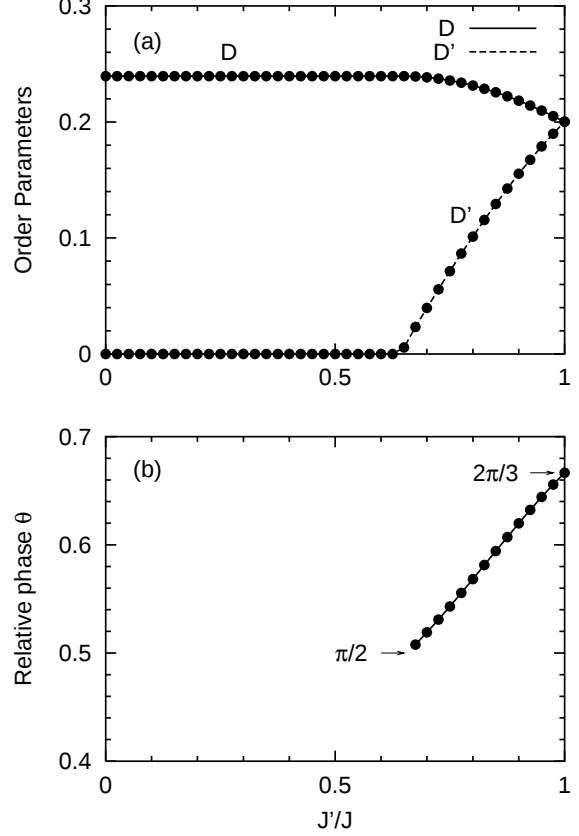


Fig. 3. J'/J dependences of (a) order parameters and (b) relative phase $\theta = \theta'$, at half-filling. See details in the text.

in the square lattice and 120-degree phase in the triangular lattice.

In Fig. 4 we show the doping dependences of the order parameters $\Delta = \Delta_x = \Delta_y = \Delta_{xy}$ and $\chi = \chi_x = \chi_y = \chi_{xy}$ determined self-consistently at $t' = t, J' = J$ and $J/t = 0.3$ (triangular lattice). Qualitatively similar figure has been obtained recently,¹⁹ but the order parameter χ has not been taken into account, which plays an important role in the gauge theories for the t - J model. As shown in Fig. 4, the superconducting region is large, which is consistent with the high-temperature expansion study for the triangular t - J model when $t > 0$. Surprisingly the superconducting region is even larger for $t < 0$, in which case the high-temperature study has shown that the ferromagnetic instability takes place for $J/t < 0.3$.²⁰ In order to clarify the actual ground state in the triangular t - J model, more careful energy comparisons including ferromagnetism as well as the 120-degrees antiferromagnetism (realized at half-filling) are necessary. In particular, there will be a competition between the ferromagnetic fluctuation and singlet formations for $J/t > 0.3$ which leads to a heavy fermion-like behavior appearing in the specific heat.¹¹ The relation to this competition and the RVB states remains a future problem. In the region with very low electron density, we expect a triplet superconductivity.

For the recently discovered superconductor, Na_xCoO_4 , the sign of t is controversial.^{19,21} If the sign is negative,

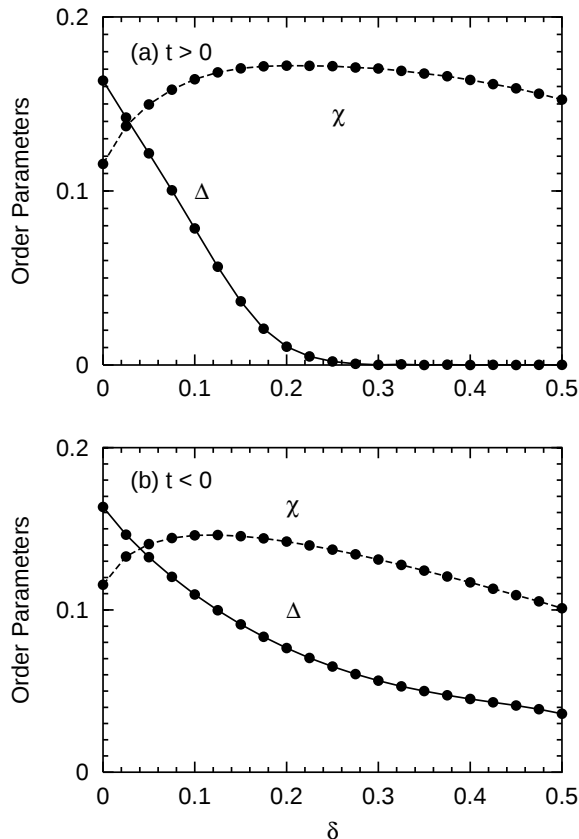


Fig. 4. Doping dependences of the order parameters in the triangular t - J model with (a) positive t and (b) negative t . $J/|t| = 0.3$.

the superconductivity is more favored. For the organic superconductors, the sign of t is negative, but in this case, the electron density is just at half-filling. In the t - J model calculation, we cannot discuss this superconductivity and instead the Hubbard model has been used to explain the superconductivity via spin-fluctuation.²²⁾ In such calculations, only $d_{x^2-y^2}$ -wave order parameter is observed. It will be an interesting problem to search for the d + i d state in the parameter close to the triangular lattice in the spin-fluctuation mechanism.

There is another competition between antiferromagnetism and superconductivity in the phase diagram shown in Fig. 2. For the Heisenberg model, Weihong et al. discussed that the commensurate antiferromagnetism is stable for $J'/J < 0.7$ using series expansion methods.²³⁾ This critical value is the same as found in Fig. 2, which means that the d + i d state probably corresponds to the spin gap state at half-filling. It is necessary to compare the energies of antiferromagnetic state and d -wave superconductivity in the phase diagram. However it is well known that the mean-field theories overestimate the magnetic states. The Gutzwiller approximation does not remedy this problem.⁸⁾ In the square lattice, the variational Monte Carlo studies have shown that the lowest variational state is a coexistent state of antiferromag-

netism and d -wave superconductivity for $\delta < 0.1$.²⁴⁻²⁶⁾ As J'/J increases and the magnetic frustration is induced, we expect that the region of antiferromagnetism

shrinks and is confined in the very vicinity of half-filling. Therefore the RVB superconducting region in Fig. 2 will safely survive. Although the detailed study on this issue is necessary, the phase diagram shown in Figs. 2 and 4 promises that an interesting time-reversal breaking superconducting state is one of the strong candidates for the ground state.

In summary we have studied the frustrating t - J model within a Gutzwiller approximation. The frustration induces a superconductivity with broken time-reversal symmetry in the parameter region close to the triangular lattice. The relative phase between the order parameters gradually changes as a function of J'/J which connects the $d_{x^2-y^2}$ -wave and typical 120-degree phase in the triangular lattice. We also discussed the SU(2) degeneracy at half-filling. We found that there is unexpectedly very large variety of states in strongly correlated frustrating systems.

The author would like to thank very useful discussions and conversations with B. S. Shastry, G. Baskaran, and T. Koretsune.

- 1) P. W. Anderson, Mat. Res. Bull. **8** (1973) 153.
- 2) P. Fazekas and P. W. Anderson, Phil. Mag. **30** (1974) 423.
- 3) P. W. Anderson, Science **235** (1987) 1196.
- 4) K. Kanoda, private communication.
- 5) K. Takada et al., Nature **422** (2003) 53.
- 6) H. Yokoyama and H. Shiba, J. Phys. Soc. Jpn. **57** (1988) 2482.
- 7) C. Gros, Phys. Rev. B **38** (1988) 931; Ann. Phys. (N.Y.) **189** (1989) 53.
- 8) F. C. Zhang, C. Gros, T. M. Rice and H. Shiba, Supercond. Sci. Technol. **1** (1988) 36.
- 9) T. Tanamoto, H. Kohno and H. Fukuyama, J. Phys. Soc. Jpn. **62** (1993) 717 and J. Phys. Soc. Jpn. **63** (1994) 2739.
- 10) H. Yokoyama and M. Ogata, J. Phys. Soc. Jpn. **65** (1996) 3615.
- 11) T. Koretsune and M. Ogata, Phys. Rev. Lett. **89** (2002) 116401.
- 12) A. Himeda and M. Ogata, J. Phys. Soc. Jpn. **66** (1997) 3367.
- 13) M. Ogata, J. Phys. Soc. Jpn. **66** (1997) 3375.
- 14) I. Affleck, Z. Zou, T. Hsu and P. W. Anderson, Phys. Rev. B **38** (1988) 745.
- 15) T. K. Lee and S. Feng, Phys. Rev. B **41** (1990) 11110.
- 16) X.-G. Wen, F. Wilczek, and A. Zee, Phys. Rev. B **39** (1989) 11413.
- 17) V. Kalmeyer, R. B. Laughlin, Phys. Rev. B **39** (1989) 11879.
- 18) P. W. Anderson, B. S. Shastry, and D. Hristopoulos, Phys. Rev. B **40** (1989) 8939.
- 19) While preparing this manuscript, we notice a similar work on the triangular lattice, G. Baskaran, cond-mat/0303649 and B. Kumar and B. S. Shastry, cond-mat/0304210.
- 20) T. Koretsune and M. Ogata, preprint.
- 21) D. J. Singh, Phys. Rev. B **61** (2000) 13397.
- 22) H. Kino and K. Kontani, J. Phys. Soc. Jpn. **67** (1998) 3691 and H. Kondo and T. Moriya, J. Phys. Soc. Jpn. **67** (1998) 3695.
- 23) Z. Weihong, R. H. McKenzie and R. R. P. Singh, Phys. Rev. B **59** (1999) 14367.
- 24) T. Giamarchi and C. Lhuillier, Phys. Rev. B **43** (1991) 12943.
- 25) A. Himeda and M. Ogata, Phys. Rev. B **60** (1999) R9935.
- 26) M. Ogata and A. Himeda, J. Phys. Soc. Jpn. **72** (2003) 374.